arXiv:1202.1908v1 [cond-mat.supr-con] 9 Feb 2012

^{13}C NMR study of superconductivity near charge instability realized in β''-(BEDT-TTF)$_4$[(H$_3$O)Ga(C$_2$O$_4$)$_3$]$\cdot$C$_6$H$_5$NO$_2$

Y. Ihara,[1,*] H. Seki,[1] and A. Kawamoto[1]

[1]*Department of Physics, Graduate School of Science, Hokkaido University, Sapporo 060-0810, Japan*

(Dated: February 10, 2012)

To investigate the superconducting (SC) state near a charge instability, we performed ^{13}C NMR experiments on the molecular superconductor β''-(BEDT-TTF)$_4$[(H$_3$O)Ga(C$_2$O$_4$)$_3$]$\cdot$C$_6$H$_5$NO$_2$, which exhibits a charge anomaly at 100 K. The Knight shift which we measured in the SC state down to 1.5 K demonstrates that Cooper pairs are in spin-singlet state. Measurements of the nuclear spin-lattice relaxation time reveal strong electron-electron correlations in the normal state. The resistivity increase observed below 10 K indicates that the enhanced fluctuation has an electric origin. We discuss the possibility of charge-fluctuation-induced superconductivity.

PACS numbers: 74.25.nj, 74.70.Kn, 75.25.Dk

Superconductivity appearing in close proximity to magnetism has fascinated researchers because of its unconventional superconducting (SC) pairing mechanisms. For example, in the Ce-based heavy fermion superconductor CeCu$_2$Si$_2$, the Cooper pairs are mediated by magnetic fluctuations that are enhanced near the magnetic quantum critical point (QCP) [1, 2]. A similar scenario has been applied to the interpretation of the SC state in high SC transition temperature cuprate, pnictide, as well as organic superconductors such as (TMTSF)$_2$PF$_6$ [3] and κ-(BEDT-TTF)$_2X$ [4, 5], and successfully explained the physical properties.

Holmes *etal.* have suggested a novel mechanism that is triggered by an increase in the SC transition temperature T_c of CeCu$_2$Si$_2$ under pressures greater than 3 GPa, at which the system approaches to the second critical point ascribed to a valence instability [6]. Theory indicates that the enhanced charge susceptibility near an *electric* QCP increase T_c. The experimental results that evidence the charge-fluctuations-induced superconductivity is required. Charge ordering is observed in several BEDT-TTF salts with α- and θ- type structures, and some of them undergo the SC transition in the charge-ordered state. A theoretical study shows that an unconventional SC state can be realized in these compounds near charge instability [7, 8], as expected for other superconductors observed near magnetic QCPs. Since resistivity and optical experiments clearly reveal the charge instability in BEDT-TTF salts, an investigation of the SC state is essential. However, few such investigations have been reported because the low $T_c (\simeq 1$ K) value has restricted detailed experiments.

Superconductivity was observed at rather high temperature reaching 9 K in β'' type structure β''-(BEDT-TTF)$_4$[(H$_3$O)M(C$_2$O$_4$)$_3$]$\cdot Y$ with $M =$ Ga, Fe and Cr and $Y =$ C$_6$H$_5$NO$_2$ or C$_6$H$_5$CN [9–12]. These compounds consist of alternating BEDT-TTF layers and anion block layers as shown in Fig. 1(a). The metallic conductivity is governed by the positive carriers injected into the two-dimensional BEDT-TTF layers. Unlike κ-(BEDT-TTF)$_2X$ near antiferromagnetism, magnetic anomaly is absent for these β'' family compounds, whereas the anomaly associated with charge ordering is observed at approximately 100 K by Raman spectroscopy and electrical transport measurements [12]. Superconductivity in these salts must be investigated experimentally to unravel the nature of superconductivity in the vicinity of the charge instability.

In addition to the interplay between charge ordering and superconductivity, the extremely high upper critical field H_{c2} of 33 T, which is almost three times the Pauli-Clogston limit, must be investigated [12]. In a magnetic field, superconductivity is suppressed by the Pauli depairing effect [13]. To sustain superconductivity in high magnetic field, an unconventional SC state is introduced by Fulde, Ferrel, Larkin and Ovchinnikov (FFLO state) [14, 15]. In the FFLO state, Pauli depairing effect is suppressed by allowing a real-space modulation of the SC gap. Another possibility is the spin-triplet SC state in which the Pauli depairing is irrelevant because Cooper pairs can preserve their spin degrees of freedom. To comprehend the high-field SC state, SC pairing symmetry must be determined from low-field experiments.

NMR spectroscopy is a powerful technique to microscopically investigate the electronic properties of both normal and SC states. Although ^{13}C NMR measurement detects only the magnetic properties, we found an anomaly associated with charge instability through the modification of the local spin susceptibility. To examine the SC properties of β'' salts, we measured the nuclear spin-lattice relaxation time (T_1) and Knight shift (K) at low temperatures.

In this Letter, we focus on the β'' salt with $M =$ Ga and $Y =$ C$_6$H$_5$NO$_2$, which exhibit superconductivity at 7.5 K. Single crystals were grown using the electrocrystallization technique as described in Ref. [10]. We obtained two single-crystal phases, either plates or needles. The crystalline parameters of the needle crystal are consistent with those reported for the SC samples [10]. Magnetization and resistivity measurements on the needle crystal

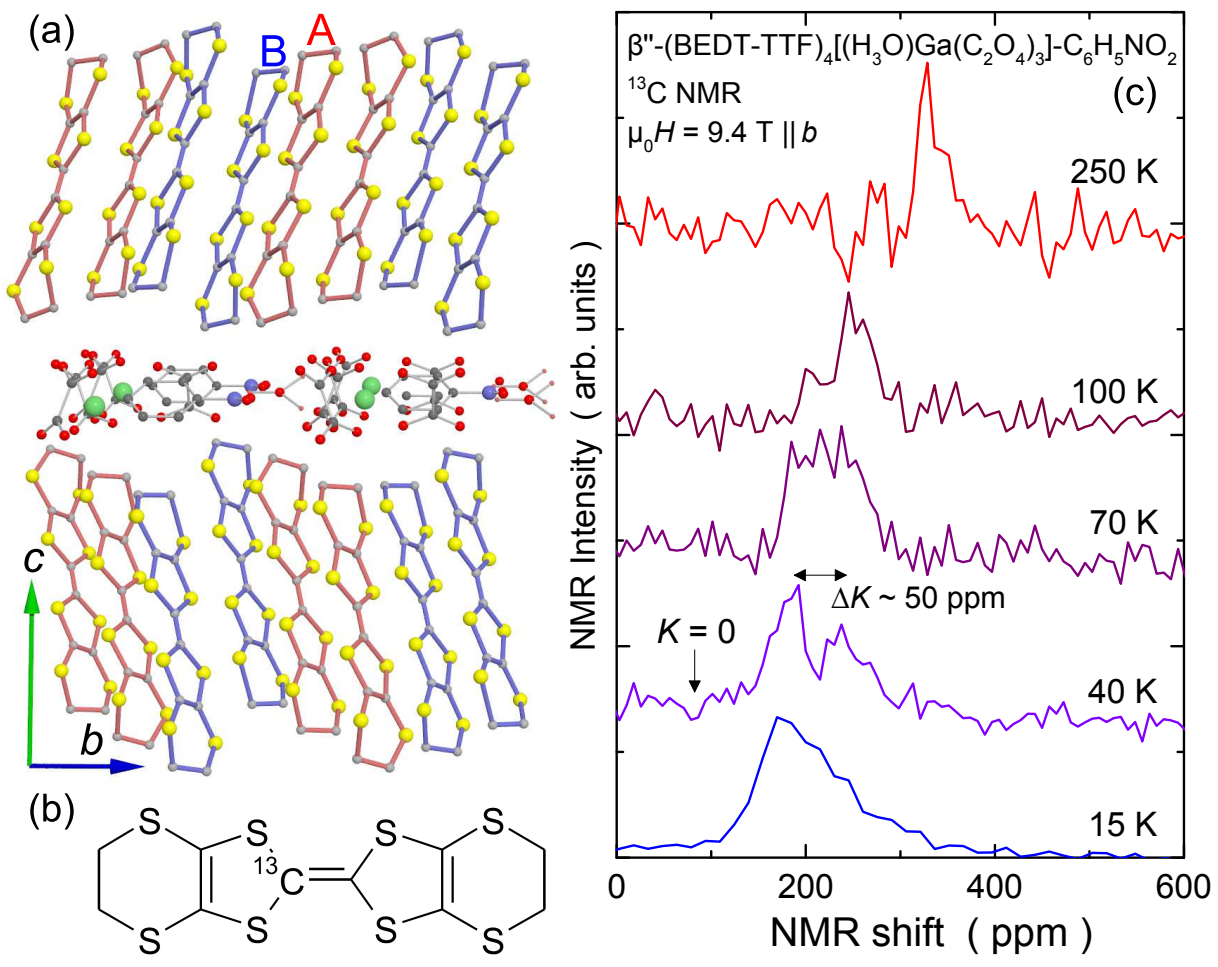

FIG. 1: (a) The crystal structure of β''-(BEDT-TTF)$_4$[(H$_3$O)Ga(C$_2$O$_4$)$_3$]·C$_6$H$_5$NO$_2$ [10] (space group $C2/c$). The inequivalent BEDT-TTF molecules denoted by A and B occupy nearly identical sites with small difference at ethylene groups. (b) The structure of our BEDT-TTF molecule. Only one side of the central C=C bond is enriched with ^{13}C isotope to suppress the Pake doublet. (c)^{13}C NMR spectra for field along b-axis. Single peak at high temperature splits into two peaks at 40 K, at which carriers are disproportionated. The spectral splitting allows us to estimate $\Delta\rho \simeq 0.2e$. $K = 0$ indicates a position determined by $\sigma = 82$ ppm (see text).

detect the SC transition at 7.5 K, in accordance with previous reports [10]. Typical dimensions of the SC needle sample are $1 \times 0.1 \times 0.2$ mm^3. The single-crystal x-ray diffraction revealed that the longest axis is parallel to the crystalline a-axis. For the NMR experiment reported in this Letter, external magnetic fields were applied along the b-axis, which is the second longest axis of the crystal. To reduce spectral broadening due to sample misalignment, ^{13}C NMR spectra were acquired for one single crystal. To measure T_1, which does not require high frequency resolution, we aligned thirty single crystals on a flat sample holder to improve the NMR signal intensity.

When neighboring ^{13}C nuclear spins are magnetically coupled, the NMR shift of the ^{13}C resonance cannot be correctly determined, because the nuclear spin-spin coupling splits it into two peaks (Pake doublet [16]). For BEDT-TTF molecules, coupling of the ^{13}C nuclei at the central C=C bond (Fig. 1 (b)) is sufficiently strong to result in this Pake-doublet problem [17]. Therefore, we eliminated the Pake doublet by the selective enrichment of one side of the central C=C bond with ^{13}C using the cross-coupling method between non-enriched ketone and ^{13}C-enriched thio-ketone forms [18].

Figure 1(c) shows ^{13}C NMR spectra measured in a magnetic field of 9.4 T. A single peak was observed at 250 K, at which the system is in a paramagnetic state. Crystallographically, β'' salts possesses eight nonequivalent ^{13}C sites in a magnetic field, which are due to the multiplication of the two nonequivalent BEDT-TTF molecules for β'' modification (A and B sites in Fig. 1(a)), and the two ^{13}C sites at the central C=C bond of each molecule, and an additional two nonequivalent molecular sites created by the external magnetic field. When the field is applied exactly along the glide plane ($\parallel b$), four NMR peaks from four nonequivalent ^{13}C sites are expected, because the later symmetry-breaking effect of the magnetic field is suppressed. The observed single-peak spectrum is a superposition of these four spectra. The absence of clear spectral splitting is due to the similarity in crystallographic sites between nonequivalent A and B molecules, which is evident from the crystal parameters.

A spectral broadening was observed at 100 K where an anomaly associated with charge ordering is detected by Raman spectroscopy [12]. The spectrum first splits into two peaks at 40 K before merging again to form a broad single peak below approximately 20 K. The progressive development of the spectral shape from 100 K down to 40 K indicates that a spatial disproportion and not perfect charge localization occurs in the carrier density at 100 K and evolves with temperatures. This scenario is also consistent with the moderate temperature dependence of the electric resistivity below 100 K [12]. The charge imbalance $\Delta\rho$ between charge-rich and poor sites can be estimated from the spectral split at 40 K. The NMR frequency shift δ is expressed in terms of the spin susceptibility (χ_s) and the chemical shift (σ) as

$$\delta = K + \sigma = A\chi_s + \sigma. \qquad (1)$$

Here, the Knight shift K is connected to χ_s through the hyperfine coupling constant A, and enables us to measure the local charge density ρ because A depends on ρ. First, because σ is specific to the BEDT-TTF molecule, we employ a chemical-shift tensor for α-(BEDT-TTF)$_2$I$_3$ [19] to evaluate σ for β''-(BEDT-TTF)$_4$[(H$_3$O)Ga(C$_2$O$_4$)$_3$]·C$_6$H$_5$NO$_2$ in the field $H \parallel b$ and find σ as 82 ppm. Next, we assume that the average split-peak position gives the formal charge of BEDT-TTF molecules ($\rho = 0.5e$), to obtain $K = 260\rho$. The charge imbalance $\Delta\rho$ is finally estimated to be $0.2e$ from the peak separation $\Delta K \simeq 50$ ppm, which is in good agreement with $\Delta\rho$ determined by Raman spectroscopy [20].

In the charge disproportionate state below 100 K, electrons are still itinerant preserving their spin degrees of freedom. We investigated the nature of electronic spin fluctuations by measuring T_1, and the results under magnetic fields of 3.6 and 7.0 T are displayed in Fig. 2. For two fields, we observed an increase in $(T_1T)^{-1}$ below 50 K down to approximately 10 K. The temperature-dependent $(T_1T)^{-1}$ contrasts starkly with the Fermi liquid behavior, which is characterized by a temperature-independent $(T_1T)^{-1}$. In general, $(T_1T)^{-1}$ is expressed

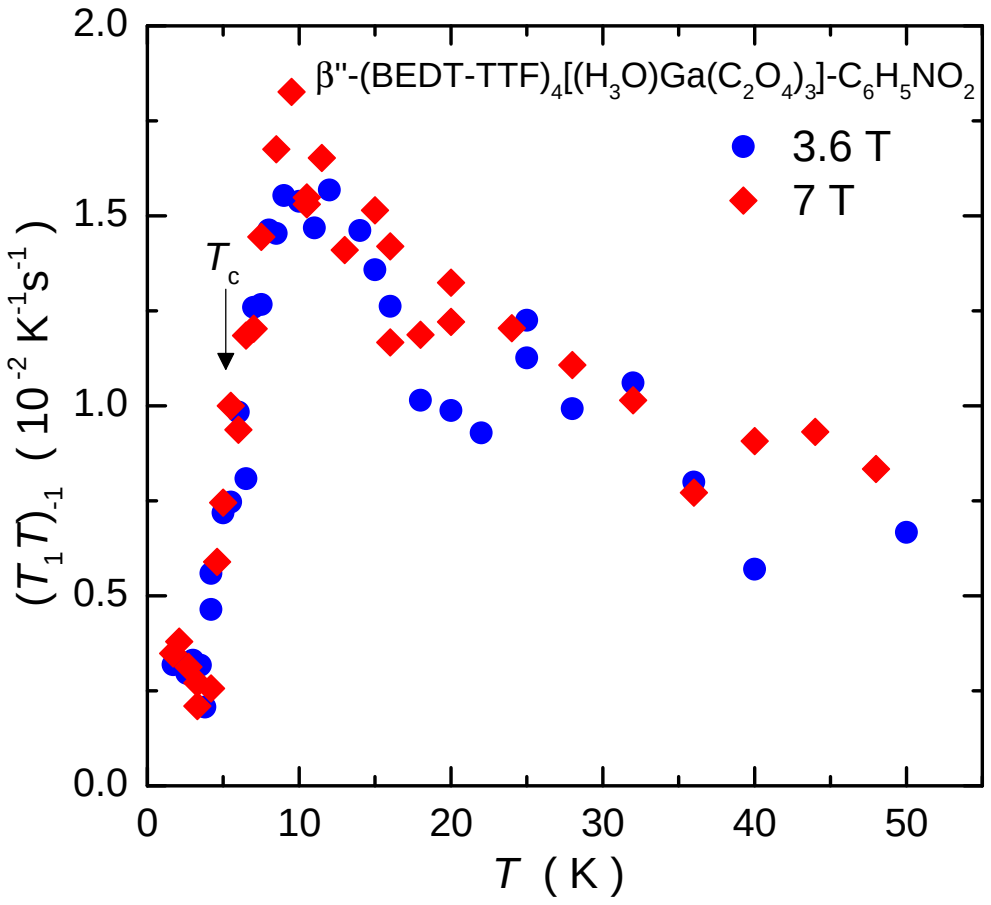

FIG. 2: Temperature dependence of $(T_1T)^{-1}$ measured at 3.6 and 7 T. In the charge disproportionate state, $(T_1T)^{-1}$ increases below 50 K down to 10 K, which indicates strong electron-electron correlations. An anomaly associated with superconductivity is barely observed at $T_c = 5.8$ K, because $(T_1T)^{-1}$ has already decreased from its peak value at 10 K.

in terms of dynamic susceptibility $\chi''(q,\omega)$ as

$$\frac{1}{T_1T} = \frac{2\gamma_n^2 k_B}{(\gamma_e \hbar)^2} \sum_q A_q A_{-q} \frac{\chi''(q,\omega)}{\omega}, \qquad (2)$$

and is increased by the enhanced magnetic fluctuations due to strong electron-electron correlations [21]. The increase in $(T_1T)^{-1}$ above T_c indicates that electron-electron correlations are strong when superconductivity sets in. In the vicinity of charge instability, the dynamic susceptibility can also be enhanced by charge fluctuations, which modify the local charge density, and accordingly, the spin density.

The nuclear spin-lattice relaxation rate measured via ^{13}C NMR can only detect fluctuating magnetic fields at the ^{13}C site, but cannot reveal their origin. Thus, we measured the in-plane resistivity as a complementary probe. A semiconducting behavior was observed in a temperature range (10 ∼ 100 K), in which $(T_1T)^{-1}$ increases, as already reported in Ref. [12], where the semiconducting behavior is interpreted as the segregation of metallic and semiconducting phases. Instead, based on the NMR-shift data shown below, we propose a uniform electronic state. The increase in resistivity below 100 K is due to the scattering of conduction electrons by low-energy charge fluctuations. For the β'' family of compounds without magnetism, enhanced charge fluctuations in the vicinity of a charge instability increase $\chi''(q,\omega)$ by spin-charge coupling. The anomaly associated with superconductivity is barely observed at T_c, because $(T_1T)^{-1}$ start decreasing at 10 K, which is much above $T_c(4\text{ T}) = 5.8$ K. We discuss the anomalous electronic state below 10 K down to T_c later. Although this anomalous state masks the SC properties, the absence of the Hebel-Slichter peak [22] slightly below T_c may indicate unconventional superconductivity.

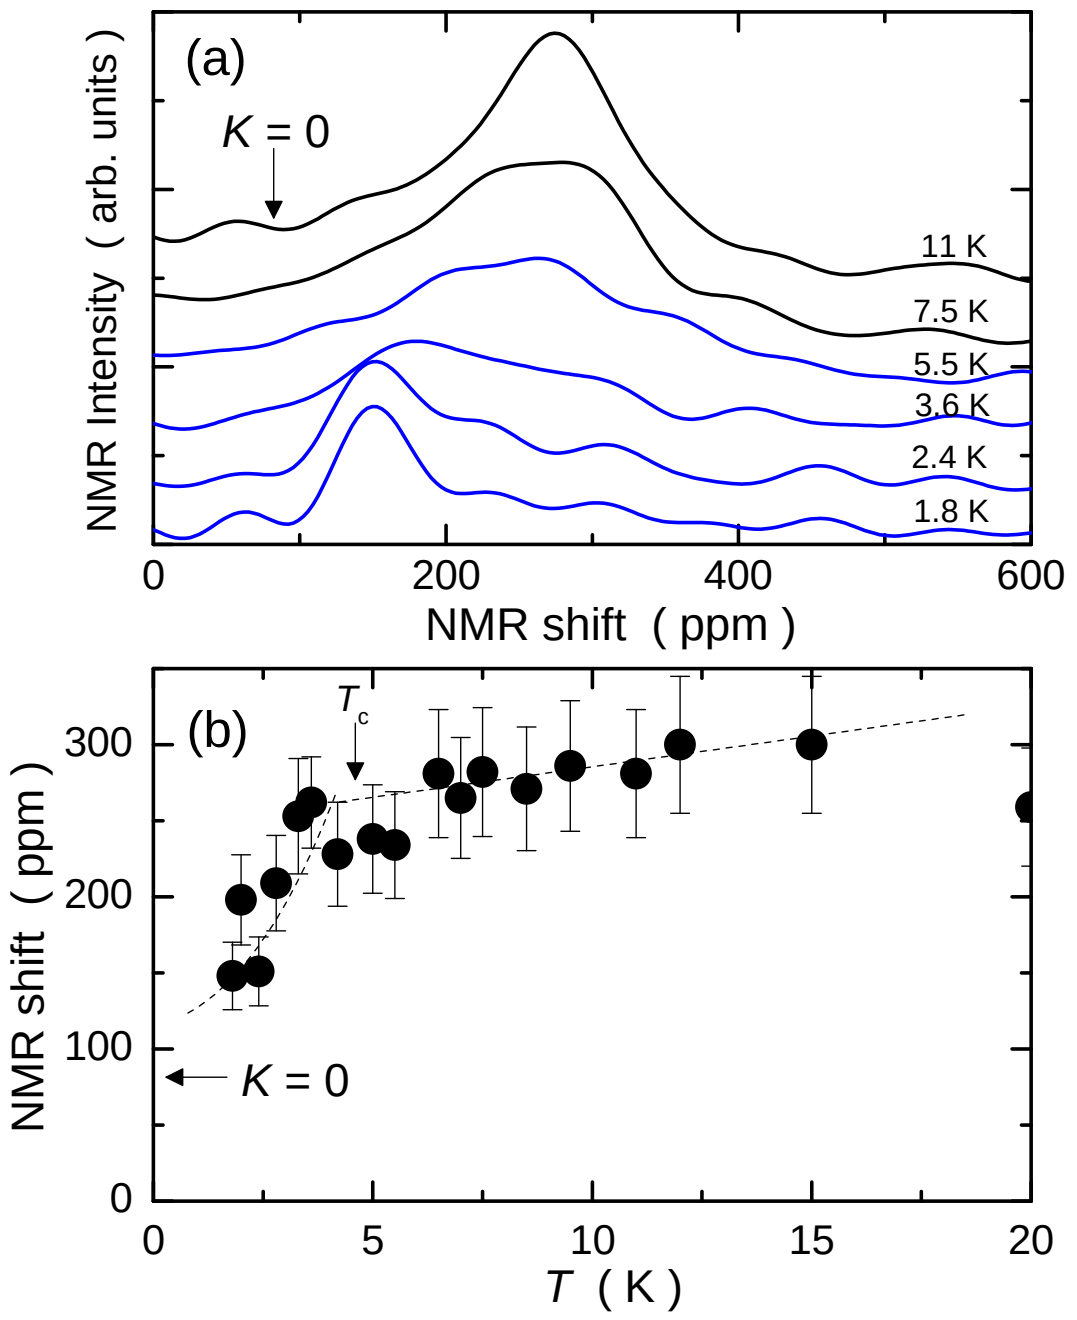

FIG. 3: (a) ^{13}C NMR spectra at low temperature for $\mu_0 H = 4.23$ T. Below T_c, the full spectral weight shifts to the position indicated by the arrow labeled $K = 0$. Disappearance of spectral weight at 300 ppm at low temperatures reveals the absence of phase segregation. (b) Temperature dependence of NMR shift determined by peak position. The dashed line is a guide to the eyes.

We detected the clear signature of SC properties (i.e., the spin symmetry of Cooper pairs) by measuring the Knight shift. Figure 3(a) shows ^{13}C NMR spectra for temperatures below 11 K. The full spectral weight has shifted below T_c, which indicates bulk superconductivity without phase separation, and therefore a uniform electronic state for the normal state. Figure 3(b) shows the temperature dependence of NMR shift determined by the peak positions. The NMR shift starts decreasing at $T_c(4\text{ T}) = 5.8$ K, and approaches approximately 100 ppm at 0 K. When the spin susceptibility completely vanishes in the SC state, the NMR shift is identical to $\sigma = 82$ ppm. The suppression of spin susceptibility below T_c and the agreement between the residual NMR shift at the lowest temperature and σ strongly suggest that spin susceptibility is almost reduced to zero in the SC state because of the formation of spin-singlet Cooper pairs. We exclude the spin-triplet scenario for the interpretation of very large value of H_{c2}. We suggest that an FFLO state may be created above the Pauli limiting field of 12 T. Therefore, a high-field NMR experiment is essential to unravel the high-field SC state.

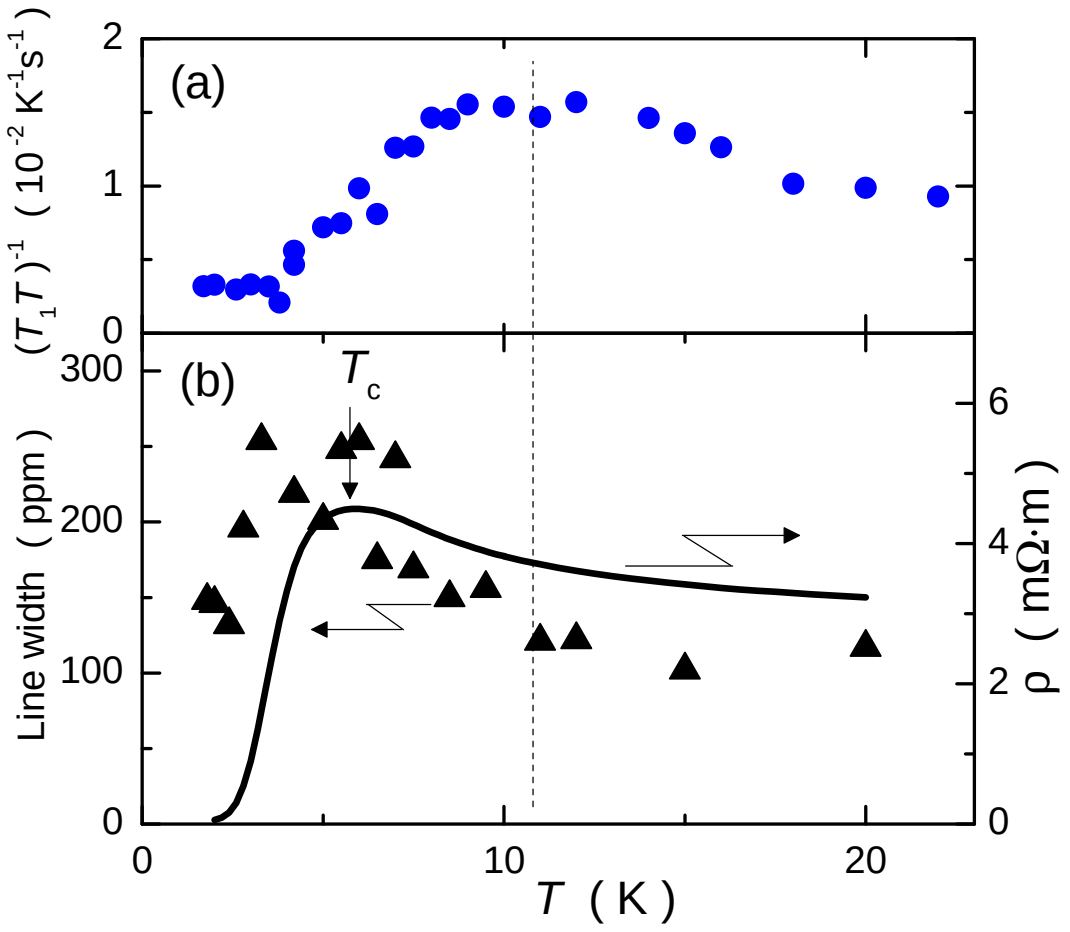

FIG. 4: (a) Magnified view of $(T_1T)^{-1}$ near T_c. (b) NMR line width (left scale) plotted together with the resistivity (right scale) measured under $\mu_0H \simeq 4$ T. An abrupt increase is observed in both the line width and resistivity below 10 K, at which $(T_1T)^{-1}$ starts decreasing. T_c(4 T) is determined to be 5.8 K from the peak in resistivity.

We now discuss the anomalous electronic state above T_c. In the temperature range $T_c < T < 10$ K, the decrease in $(T_1T)^{-1}$ is accompanied by an abrupt increase in resistivity and the spectral width, as indicated by the dashed line in Fig. 4. Moreover, this increase in the resistivity has been observed in the magneto-resistance at the corresponding temperatures[12]. The decrease in $(T_1T)^{-1}$ could be interpreted as the suppression of the density of states (DOS) by preformed SC pairs as is suggested for high-T_c cuprate superconductors, and κ-(BEDT-TTF)$_2X$. However, the invariance of $(T_1T)^{-1}$ data in magnetic fields of up to 7 T, which are strong enough to suppress T_c by approximately 30 %, demonstrates clearly that the precursor of SC instability is irrelevant. Instead, we suggest that the normal state DOS is suppressed by a gap in a part of Fermi surface, which is induced by strong electron-electron correlations.

The suppression of the normal-state DOS cannot increase the spectral width. We propose an incommensurate distribution of the local susceptibility as the origin of the spectral broadening below 10 K. The mechanisms resulting in the 10-K anomaly is different from that for the 100-K anomaly. The clear spectral splitting, which appears below 100 K in Raman and NMR spectra, indicates that the charge disproportion is commensurate with the crystalline lattice. The origin of the commensurate charge ordering is often ascribed to the off-site Coulomb interaction, whereas the enhanced charge susceptibility by Fermi-surface nesting can result in an incommensurate charge ordering. We underline that the low-temperature anomaly is caused by the Fermi-surface nesting, and superconductivity occurring subsequently could be induced by the enhanced charge fluctuations. Further experimental and theoretical studies on superconductivity in β''-(BEDT-TTF)$_4$[(H$_3$O)Ga(C$_2$O$_4$)$_3$]·C$_6$H$_5$NO$_2$ will reveal the physics at work near charge criticality.

To conclude, we have performed a ^{13}C NMR experiment on single-crystal samples, and found that spin-singlet superconductivity occurs in the charge disproportionate state. Because we can exclude the suppression of Pauli depairing effect by parallel-spin pair formation, we suggest an FFLO state for the high-field SC state. The increase in $(T_1T)^{-1}$ below 50 K down to 10 K provides an evidence that the electrons are strongly correlated in the normal state. At temperatures above T_c, we also observed a low-temperature anomaly in $(T_1T)^{-1}$, the NMR line width, and resistivity, and highlighted the importance of charge fluctuations in understanding superconductivity in β''-(BEDT-TTF)$_4$[(H$_3$O)Ga(C$_2$O$_4$)$_3$]·C$_6$H$_5$NO$_2$.

We acknowledge T. Inabe for the x-ray diffraction experiment and H. Kato for the resistivity measurement. This work was partially supported by Grant-in-Aid for Young Scientists (B) (No.23740249).

---

* yihara@sci.phys.hokudai.ac.jp

[1] F. Steglich, J. Aarts, C. D. Bredl, W. Lieke, D. Meschede, W. Franz, and H.Schäfer, Phys. Rev. Lett **43,** 1892 (1979).

[2] N. D. Mathur, F. M. Grosche, S. R. Julian, I. R. Walker, D. M. Freye, R. K. W. Haselwimmer, and G. G. Lonzarich, Nature **394,** 39 (1998).

[3] D. Jérome, A. Mazaud, M. Ribault, and K. Bechgaard, J. Phys. Lett. (Paris) **41,** L95 (1980).

[4] J. M. Williams, A. J. Schultz, U. Geiser, K. D. Carlson, A. M. Kini, H. H. Wang, Wai-kwong Kwok, Myung-Hwan Whangbo, and J. E. Schirber, Science **252,** 1501 (1991).

[5] S. Murakami and N. Nagaosa, J. Phys. Soc. Jpn. **69,** 2395 (2000).

[6] A. T. Holmes, D. Jaccard, and K. Miyake, Phys. Rev. B **69,** 024508 (2004).

[7] J. Merino and R. H. McKenzie, Phys. Rev. Lett. **87,** 237002 (2001).

[8] J. Merino, A. Greco, N. Drichko, and M. Dressel, Phys. Rev. Lett. **96,** 216402 (2006).

[9] M. Kurmoo, A. W. Graham, P. Day, S. J. Coles, M. B. Hursthouse, J. L. Caulfield, J. Singleton, F. L. Pratt, W. Hayes, L. Ducasse and P. Guionneau, J. Am. Chem. Soc. **117,** 12209 (1995).

[10] H. Akutsu, A. Akutsu-Sato, S. S. Turner, D. Le Pevelen, P. Day, V. Laukhin, A-K. Klehg, J. Singleton, D. A. Tocher, M. R. Probert and J. A. K. Howard, J. Am. Chem. Soc. **124,** 12430 (2002).

[11] A. I. Coldea, A. F. Bangura, J. Singleton, A. Ardavan, A. Akutsu-Sato, H. Akutsu, S. S. Turner and P. Day, Phys. Rev. B **69,** 085112 (2004).

[12] A. F. Bangura, A. I. Coldea, J. Singleton, A. Ardavan, A. Akutsu-Sato, H. Akutsu, S. S. Turner, P. Day, T. Yamamoto and K. Yakushi, Phys. Rev. B **72,** 014543

(2005).

[13] A. M. Clogston, Phys. Rev. Lett. **9,** 266 (1962).

[14] P. Fulde and A. Ferrel, Phys. Rev. **135,** A550 (1964).

[15] A. I. Larkin and Yu. N. Ovchinnikov, Sov. Phys. JETP **20,** 762 (1965).

[16] G. E. Pake, J. Chem. Phys. **16** 327 (1948).

[17] A. Kawamoto, K. Miyagawa, Y. Nakazawa, and K. Kanoda, Phys. Rev. B **52,** 15522 (1995).

[18] M. Yamashita, A. Kawamoto and K. Kumagai, Synth. Met. **133-134,** 125 (2003).

[19] T. Kawai and A. Kawamoto, J. Phys. Soc. Jpn. **78,** 074711 (2009).

[20] T. Yamamoto, H. M. Yamamoto, R. Kato, M. Uruichi, K. Yakushi, H. Akutsu, A. Sato-Akutsu, A. Kawamoto, S. S. Turner and P. Day, Phys. Rev. B **77,** 205120 (2008).

[21] T. Moriya, J. Mag. Mag. Mat. **100,** 261 (1991).

[22] L. C. Hebel and C. P. Slichter, Phys. Rev. **113,** 1504 (1959).